

**PREPARATION, CHARACTERIZATION AND
SOME BIOLOGICAL ACTIVITIES OF WATER
SOLUBLE CHITOSAN DERIVATIVES**

By

ESRA SULIMAN KHALIL SULIMAN

**Thesis submitted in fulfillment of the requirements
for the degree of Doctor of Philosophy**

October 2015

DEDICATION

TO the memories of my beloved mother (SAYDAH)

TO my dear father

TO my husband and my children

TO my sisters and brothers

ACKNOWLEDGMENTS

Firstly, I owe it all to Almighty God for granting me the wisdom, health and strength to undertake this research task and enabling me to its completion.

I would like to express my sincere and deep appreciation and gratitude to my supervisor **Dato' Professor Muhammad Idiris Saleh** for his wise guidance, intellectual support, stimulating discussions and inspiring words. His encouraging attitudes through several years of valuable guidance have enriched me with empirical insight and expertise for my scientific and academic career. I also thank my co-supervisor Prof. Bahruddin Saad for his valuable advice, scholarly inputs and encouragement.

I would like to thank the Dean of the Chemical Science, Prof. Wan Ahmad Kamil Mahmood, who has always been keen to nurture a conducive academic environment. My thanks go to the staff members at the School of Chemical Science, Universiti Sains Malaysia (USM), have been very kind enough to extend their help to various phases of this research. My thanks go to Dr El-Sayed Moussa Negim. I would also like to thank the Dean and staff of School of Pharmaceutical Science and Biological Science for providing some of the facilities for anticancer and antibacterial testings of my compounds.

I would also like to thank Organization for Women in Science for the Developing World (O W S D W) and Swedish International Development Cooperation Agency Fellowships. Many people who I cannot mention one by one deserve thanks and appreciation for their support in the preparation of my thesis.

Finally, my best regards are to my father Suliman Khalil, who loves provided my inspiration and helped me at every stage of my personal and academic life. To my great husband Dr. Mohammed Khalil for the encouragement, patience and supportive in every possible way to see the completion of this work, words cannot express my appreciation to him. To my lovely daughters and son Aseel, Raheeq and Khalil, to my sisters and brothers for their love and best wishes, encouragement and assistance throughout this academic journey.

Esra Suliman
Penang, Malaysia. 2015

TABLE OF CONTENTS

Page

DEDICATION	
ACKNOWLEDGEMENTS	ii
TABLE OF CONTENTS	iii
LIST OF TABLES	xi
LIST OF FIGURES	xii
LIST OF SCHEMES	xviii
LIST OF SYMBOLS	xx
LIST OF MAJOR ABBREVIATIONS	xxi
ABSTRAK	xxiv
ABSTRACT	xxvi
CHAPTER 1 : INTRODUCTION	1
1.1 Chitosan	1
1.1.1 Production of Chitosan	2
1.1.2 Properties of Chitosan	3
1.1.2.1 Molecular Weight	4
1.1.2.2 Degree of Deacetylation	4
1.1.2.3 Solubility of Chitosan	5
1.1.2.4 Viscosity	6
1.1.2.5 Biological Properties of Chitosan	7
1.1.2.5.1 Biodegradability	7
1.1.2.5.2 Biocompatibility	9
1.1.2.5.3 Toxicity	9

1.2	Previous Studies on Modification and Applications of Chitosan	9
1.2.1	Chemically Modified Chitosan	10
1.2.1.1	Alkylated Derivatives of Chitosan	10
1.2.1.2	Acylation Derivatives of Chitosan	11
1.2.1.3	Thiolation of Chitosan	12
1.2.1.4	Grafting of Chitosan	12
1.3	Applications of Chitosan	15
1.3.1	Anticancer Properties	16
1.3.2	Antimicrobial Activity of Chitosan	19
1.3.2.1	Determination of Chitosan Antimicrobial Activities	22
1.3.2.2	Factors Affecting the Antimicrobial Activity	24
1.3.2.2.1	Intrinsic Factors	24
1.3.2.2.2	Extrinsic Factors	25
1.4	The Motivation of Research	26
1.5	Research Objectives	28
1.6	Organization of the Thesis	28
	CHAPTER 2: METHODOLOGY	29
2.1	Material and Equipments	29
2.1.1	Materials	29
2.1.2	Equipments	30
2.1.2.1	Fourier Transform Infra-Red Spectroscopy (FT-IR)	30
2.1.2.2	Nuclear Magnetic Resonance (NMR)	30
2.1.2.3	CHN Elemental Analyzer	30
2.1.2.4	Differential Scanning Calorimeter (DSC)	30

2.1.2.5	Thermogravimetric Analysis (TGA)	31
2.1.2.6	Gel Permeation Chromatography (GPC)	31
2.1.2.7	Scanning Electron Microscopy (SEM)	31
2.1.2.8	X-Ray Diffraction (XRD)	31
2.1.2.9	Photoluminescence (PL) Measurements	32
2.1.2.10	Microplate Reader	32
2.2	Methods	32
2.2.1	Synthesis of Water-Soluble Chitosan Derivatives	32
2.2.1.1	(2-Cyanoguanidine) dicyandiamide Chitosan (CS-DCDA)	32
2.2.1.1.1	2-Aminopyridine (2-cyanoguanidine) dicyandiamide Chitosan (CS-APDCD)	33
2.2.1.2	Poly(1-vinylpyrrolidone-co-2-dimethylaminoethyl methacrylate) Chitosan (CS-VPDMAEM)	34
2.2.1.3	4,7,10-Trioxa-1,13-tridecanediamine Chitosan (CS-OXAM)	35
2.2.1.4	Bis(2-chloroethyl) ether Chitosan (CS-BCOE)	35
2.2.1.5	L- Phenylalanine (2-amino-3-phenylpropanoic acid) Chitosan (CS-PhAL)	36
2.2.1.6	2-Aminopyridine Chitosan (CS-2AP)	37
2.2.1.7	Resorcinol (benzen-1,3-diol) Chitosan (CS-RES)	37
2.2.1.8	8-Hydroxyquinoline (oxine) Chitosan (CS-HQ)	38
2.2.1.9	4-Methylphenol (p-cresol) Chitosan (CS-mPhenol)	38
2.2.1.10	Polycrylamide Chitosan (CS-AM)	39
2.2.1.10.1	L-Phenylalanine (2-amino-3-phenylpropanoic acid) Polyacrylamide Chitosan (CS-PhALAM)	39
2.2.1.10.2	2-Aminopyridine Polyacrylamide Chitosan (CS-APAM)	40

2.2.1.10.3 Resorcinol (benzen-1,3-diol) Polyacrylamide Chitosan (CS-RESAM)	41
2.2.1.10.4 4-Methoxyaniline (<i>p</i> -anisidine) Polyacrylamide Chitosan (CS-MEOXANAM)	41
2.2.2 Anticancer Applications (<i>In vitro</i>)	42
2.2.3 Antibacterial Applications	43
2.2.3.1 Determination of Minimum Inhibitory Concentration (MIC)	43
2.2.3.1.1 Preparation of Broth Culture	44
2.2.3.1.2 Preparation of Substances Test Concentrations in 96 Well Microtiter Plate	44
CHAPTER 3: RESULTS AND DISCUSSION	46
3.1 Characterization of Chitosan Derivatives	46
3.1.1 Introduction	46
3.1.2 FT-IR and NMR Analysis	47
3.1.2.1 FT-IR Spectra of Chitosan	47
3.1.2.2 FT-IR of Dicyandiamide Chitosan (CS-DCDA)	48
3.1.2.3 NMR Analysis of Dicyandiamide Chitosan (CS-DCDA)	49
3.1.2.4 FT-IR Analysis of 2-Aminopyridine Dicyandiamide Chitosan (CS-APDCDA)	52
3.1.2.5 NMR Analysis of 2-Aminopyridine Dicyandiamide Chitosan (CS-APDCDA)	53
3.1.2.6 FT-IR of Poly(1-vinyl pyrrolidone-co-2-dimethylaminoethyl methacrylate) Chitosan (CS-VPDMAEM)	56
3.1.2.7 NMR Analysis of Poly (1-vinyl pyrrolidone-co-2-dimethyl amino ethyl methacrylate) Chitosan (CS-VPDMAEM)	57
3.1.2.8 FT-IR of 4,7,10 -Trioxa-1,13-tridecanediamine Chitosan (CS-OXAM)	60

3.1.2.9 NMR Analysis of 4,7,10–Trioxa-1,13-tridecanediamine Chitosan (CS-OXAM)	61
3.1.2.10 FT-IR Analysis of Bis(2-chloroethyl) ether Chitosan (CS-BCOE)	64
3.1.2.11 NMR Analysis of Bis(2-chloroethyl) ether Chitosan (CS-BCOE)	65
3.1.2.12 FT-IR of Phenylalanine Chitosan (CS-PhAL)	68
3.1.2.13 NMR Analysis of Phenylalanine Chitosan (CS-PhAL)	69
3.1.2.14 FT-IR of 2-Aminopyridine Chitosan (CS-2AP)	72
3.1.2.15 NMR Analysis of 2-Aminopyridine Chitosan (CS-2AP)	73
3.1.2.16 FT-IR of Resorcinol Chitosan (CS-RES)	76
3.1.2.17 NMR Analysis of Resorcinol Chitosan (CS-RES)	77
3.1.2.18 FT- IR of 8-Hydroxyquinoline Chitosan (CS-HQ)	80
3.1.2.19 NMR Analysis of 8-Hydroxyquinoline (CS-HQ)	81
3.1.2.20 FT- IR of 4-Methylphenol Chitosan (CS-mPhenol)	84
3.1.2.21 NMR of 4-Methylphenol Chitosan (CS-mPhenol)	85
3.1.2.22 FT-IR Analysis of Polyacrylamide Chitosan (CS-AM)	88
3.1.2.23 NMR Analysis of Polyacrylamide Chitosan (CS-AM)	89
3.1.2.24 FT-IR Analysis of Phenylalanine Polyacrylamide Chitosan (CS-PhALAM)	92
3.1.2.25 NMR Analysis of Phenylalanine Polyacrylamide Chitosan (CS-PhALAM)	93
3.1.2.26 FT-IR Analysis of 2-aminopyridine Polyacrylamide Chitosan (CS-APAM)	97
3.1.2.27 NMR Analysis of 2-aminopyridine Polyacrylamide Chitosan(CS-APAM)	98
3.1.2.28 FT-IR Analysis of Resorcinol Polyacrylamide Chitosan (CS-RESAM)	101

3.1.2.29 NMR Analysis of Resorcinol Polyacrylamide Chitosan (CS-RESAM)	102
3.1.2.30 FT-IR analysis of 4-Methoxyaniline polyacrylamide Chitosan (CS-MOXANAM)	106
3.1.2.31 NMR Analysis of 4-Methoxyaniline Polyacrylamide Chitosan (CS-MEOXANAM)	107
3.1.3 Degree of Deacetylation (DDA) and Degree of Acetylation (DA)	111
3.1.4 CHN Elemental Analysis and Gel Permeation Chromatography (GPC)	111
3.1.5 Solubility of Chitosan Derivatives	114
3.1.6 Thermogravimetric Analysis (TGA)	115
3.1.6.1 TGA of Chitosan	115
3.1.6.2 TGA of Dicyandiamide Chitosan	115
3.1.6.3 TGA of Poly(1-vinyl pyrrolidone-co-2-dimethylaminoethyl methacrylate) Chitosan (CS-VPDMAEM)	116
3.1.6.4 TGA of 4,7,10 -Trioxa-1,13-tridecanediamine Chitosan (CS-OXAM)	117
3.1.6.5 TGA of Bis(2-chloroethyl) ether Chitosan (CS-BCOE)	118
3.1.6.6 TGA of Phenylalanine Chitosan (CS-PhAL)	119
3.1.6.7 TGA of 2-Aminopyridine Chitosan (CS-2AP)	120
3.1.6.8 TGA of 2-Aminopyridine Dicyandiamide Chitosan (CS-2AP)	121
3.1.6.9 TGA of Resorcinol Chitosan (CS-RES)	122
3.1.6.10 TGA of 8-Hydroxyquinoline Chitosan (CS-HQ)	123
3.1.6.11 TGA of 4-Methylphenol Chitosan (CS-mPhenol)	124
3.1.6.12 TGA of Polyacrylamide Chitosan (CS-AM)	125
3.1.6.13 TGA of Phenylalanine and Polyacrylamide Chitosan (CS-PhALAM)	126

3.1.6.14 TGA of 2-Aminopyridine Polyacrylamide Chitosan (CS-APAM)	127
3.1.6.15 TGA of Resorcinol and Polyacrylamide Chitosan (CS-RESAM)	128
3.1.6.16 TGA of 4-Methoxyaniline Polyacrylamide Chitosan (CS-MEOXANAM)	129
3.1.7 Differential Scanning Calorimetry (DSC)	130
3.1.7.1 DSC of Chitosan	130
3.1.7.2 DSC of Dicyandiamide Chitosan (CS-DCDA)	131
3.1.7.3 DSC of Poly(1-vinylpyrrolidone-co-2-dimethylamino jethyl methacrylate) Chitosan (CS-VPDMAEM)	132
3.1.7.4 DSC Thermogram of 4,7,10-Trioxa-1,13-tridecanediamine Chitosan (CS-OXAM)	133
3.1.7.5 DSC Thermogram of Bis(2-chloroethyl) ether Chitosan (CS-BCOE)	134
3.1.7.6 DSC of Phenylalanine Chitosan (CS-PhAL)	135
3.1.7.7 DSC of 2-Aminopyridine Chitosan (CS-2AP)	135
3.1.7.8 DSC of 2-Aminopyridine Dicyandiamide Chitosan (CS-APDCDA)	136
3.1.7.9 DSC of Resorcinol Chitosan (CS-RES)	137
3.1.7.10 DSC of 8-Hydroxyquinoline Chitosan (CS-HQ)	138
3.1.7.11 DSC 4-Methylphenol Chitosan (CS-mPhenol)	149
3.1.7.12 DSC of Polyacrylamide Chitosan (CS-AM)	140
3.1.7.13 DSC of Phenylalanine Polyacrylamide Chitosan (CS-PhALAM)	141
3.1.7.14 DSC of 2-Aminopyridine Polyacrylamide Chitosan (CS-APAM)	142
3.1.7.15 DSC of Resorcinol Polyacrylamide Chitosan (CS-RESAM)	143

3.1.7.16 DSC of 4-Methoxyaniline Polyacrylamide Chitosan (CS-MEOXANAM)	144
3.1.8 The Surface Morphology Analysis	145
3.1.9 Characterization of the Structural Properties by XRD Technique	149
3.1.10 Investigation of the Optical Properties by Photoluminescence Spectroscopy	150
3.2 Biological Activities of Chitosan Derivatives	156
3.2.1 Introduction	156
3.2.2 Anticancer Activities of Chitosan Derivatives	156
3.2.3 Antibacterial Activity of Chitosan Derivatives	160
CHAPTER 4: CONCLUSION AND FUTURE WORKS	163
4.1 Conclusion	163
4.2 Original Contributions	164
4.3 Future Works	165
REFERENCES	167
APPENDIX 1	182
LIST OF PUBLICATIONS AND PRESENTATIONS	184

LIST OF TABLES

Page

Table 1.1	Contents of chitin from natural resources as reported by Kurita	2
Table 3.1	Elemental Analysis, DDA and DA for chitosan and chitosan derivatives	113
Table 3.2	GPC results for chitosan and chitosan derivatives	113
Table 3.3	Results of solubility for chitosan derivatives and chitosan in water	114
Table 3.4	The cytotoxic effect of synthesized compounds on colon, prostate and breast cancer cell lines	153
Table 3.5	IC ₅₀ values of most active compounds and standard drugs	159
Table 3.6	The MIC for chitosan derivatives at neutral pH 7	162

LIST OF FIGURES		Page
Figure 1.1	Structures of (a) chitin and (b) chitosan	1
Figure 1.2	Isolation of chitin and synthesis of chitosan as reported by Olteanu	3
Figure 1.3	Techniques for derivatization of chitosan	15
Figure 3.1	FT-IR spectrum of chitosan	48
Figure 3.2	FT-IR spectrum of CS-DCDA	49
Figure 3.3	¹ H-NMR spectra of (a) chitosan, (b) CS-DCDA and (c) DCDA	50
Figure 3.4	H-H COSY of CS-DCDA	50
Figure 3.5	¹³ C-NMR spectra of (a) chitosan, (b) CS-DCDA and (c) DCDA (c)	51
Figure 3.6	The HMQC for CS-DCDA	52
Figure 3.7	FT-IR spectrum of CS-APDCDA	53
Figure 3.8	¹ H-NMR spectra of (a) CS-DCDA, (b) CS-APDCDA and (c) AP (c)	54
Figure 3.9	H-H COSY of CS-APDCDA	54
Figure 3.10	¹³ C-NMR spectra of (a) CS-DCDA, (b) CS-APDCDA and (c) APA	55
Figure 3.11	The HMQC for CS-APDCDA	56
Figure 3.12	IR spectrum of CS-VPDMAEM	57
Figure 3.13	¹ H-NMR spectra of (a) chitosan, (b) CS-VPDMAEM and (c) VPDMAEM	58
Figure 3.14	H-H COSY of CS-VPDMAEM	58
Figure 3.15	¹³ C-NMR spectra of (a) chitosan, (b) CS-VPDMAEM and (c) VPDMAEM	59
Figure 3.16	The HMQC for CS-VPDMAEM	60
Figure 3.17	FT-IR spectrum of CS-OXAM	61

Figure 3.18	¹ H-NMR spectra of (a) chitosan, (b) CS-OXAM and (c) 4, 7, 10-trioxa-1,13-tridecanediamine	62
Figure 3.19	H-H COSY of CS-OXAM	62
Figure 3.20	¹³ C-NMR spectra of (a) chitosan, (b) CS-OXAM and (c) 4,7,10-trioxa-1,13-tridecanediamine	63
Figure 3.21	The HMQC for CS-OXAM	64
Figure 3.22	FT-IR spectrum of CS-BCOE	65
Figure 3.23	¹ H-NMR spectra of (a) chitosan, (b) CS-BCOE and (c) bis (2-chloroethyl)	66
Figure 3.24	H-H COSY of CS-BCOE	66
Figure 3.25	¹³ C-NMR spectra of (a) chitosan, (b) CS-BCOE and (c) bis(2-chloroethyl) ether (c)	67
Figure 3.26	The HMQC for CS-BCOE	68
Figure 3.27	FT-IR spectrum of CS-PhAL	69
Figure 3.28	¹ H-NMR spectra of (a) chitosan, (b) CS-PhAL and (c) phenylalanine	70
Figure 3.29	H-H COSY of CS-PhAL	70
Figure 3.30	¹³ C-NMR spectra of (a) chitosan, (b) CS-PhAL and (c) phenylalanine	71
Figure 3.31	The HMQC of CS-PhAL	72
Figure 3.32	FT-IR spectrum of CS-2AP	73
Figure 3.33	¹ H-NMR spectra of (a) chitosan, (b) CS-2AP and (c) 2-aminopyridine (c)	74
Figure 3.34	H-H COSY of CS-2AP	74
Figure 3.35	¹³ C-NMR spectra of (a) chitosan, (b) CS-2AP and (c) 2-aminopyridine	75
Figure 3.36	The HMQC of CS-2AP	76
Figure 3.37	FT-IR spectrum of CS-RES	77

Figure 3.38	¹ H-NMR spectra of (a) chitosan, (b) CS-RES and (c) resorcinol	78
Figure 3.39	H-H COSY of CS-RES	78
Figure 3 .40	¹³ C-NMR spectra of (a) chitosan, (b) CS-RES and (c) resorcinol	79
Figure 3 .41	HMQC for CS-RES	80
Figure 3 .42	FT-IR spectrum of CS-HQ	81
Figure 3 .43	¹ H-NMR spectra for (a) chitosan, (b) CS-HQ and (c) 8-hydroxyquinoline	82
Figure 3 .44	H-H COSY for CS-HQ	82
Figure 3 .45	¹³ C-NMR spectra for (a) chitosan, (b) CS-HQ and (c) 8-hydroxyquinoline	83
Figure 3 .46	HMQC for CS-HQ	84
Figure 3 .47	FT-IR spectrum of CS-mPhenol	85
Figure 3 .48	¹ H-NMR spectra of (a) chitosan and (b) CS-mPhenol and (c) 4-methylphenol	86
Figure 3 .49	COSY for CS-mPhenol	86
Figure 3 .50	¹³ C-NMR spectra of (a) chitosan, (b) CS-mPhenol and (c) 4-methylphenol.	87
Figure 3 .51	HMQC for CS-mPhenol	88
Figure 3 .52	FT-IR spectrum of CS-AM	89
Figure 3 .53	¹ H-NMR spectra of (a) chitosan and (b) CS-AM	90
Figure 3 .54	H-H COSY for CS-AM	90
Figure 3 .55	¹³ C-NMR spectra of (a) chitosan and (b) CS-AM	91
Figure 3 .56	The HMQC for CS-AM	92
Figure 3 .57	FT-IR spectra of (a) chitosan, (b) CS-AM and (c) CS-PhALAM	93
Figure 3 .58	¹ H-NMR spectra of (a) CS-AM, (b) CS-PhALAM and (c) phenylalanine	94

Figure 3 .59	H-H COSY for CS-PhALAM	95
Figure 3 .60	¹³ C-NMR spectra of (a) CS-AM, (b) CS-PhALAM and (c) phenylalanine	96
Figure 3 .61	The HMQC for CS-PhALAM	96
Figure 3 .62	FT- IR spectra of (a) chitosan, (b) CS-AM and (c) CS-APAM	98
Figure 3 .63	¹ H-NMR spectra of CS-AM (a), CS-APAM (b) and 2-aminopyridine (c)	99
Figure 3 .64	H-H COSY for CS-APAM	99
Figure 3 .65	¹³ C-NMR spectra of CS-AM (a), CS-APAM(b) and 2-aminopyridine (c)	100
Figure 3 .66	The HMQC of CS-APAM	101
Figure 3 .67	FT-IR spectra of (a) chitosan, (b) CS-AM and (c) CS-RESAM	102
Figure 3 .68	¹ H-NMR spectra of (a) CS-AM, (b) CS-RESAM and (c) resorcinol	103
Figure 3 .69	H-H COSY for CS-RESAM	104
Figure 3 .70	¹³ C-NMR spectra of CS-AM (a), CS-RESAM (b) and resorcinol (c)	105
Figure 3 .71	The HMQC for CS-RESAM	106
Figure 3 .72	FT-IR spectra of (a) chitosan, (b) CS-AM and (c) CS-MEOXANAM	107
Figure 3 .73	¹ H-NMR spectra of CS-AM (a), CS-MEOXANAM (b) and 4-methoxy aniline (c)	108
Figure 3 .74	H-H COSY for CS-MEOXANAM	109
Figure 3 .75	¹³ C-NMR spectra of CS-AM (a), CS-MEOXANAM (b) and 4-methoxy aniline (c)	110
Figure 3 .76	The HMQC for CS-MEOXANAM	110
Figure 3 .77	Thermogram of Chitosan	115

Figure 3 .78	Thermogram of CS-DCDA	116
Figure 3 .79	Thermogram of CS-VPDMAEM	117
Figure 3 .80	Thermogram of CS-OXAM	118
Figure 3 .81	Thermogram of CS-BCOECS	119
Figure 3 .82	Thermogram of CS-PhAL	120
Figure 3 .83	Thermogram of CS-2AP	121
Figure 3 .84	Thermogram of CS-APDCDA	122
Figure 3 .85	Thermogram of CS-RES	123
Figure 3 .86	Thermogram of CS-HQ	124
Figure 3 .87	Thermogram of CS-mPhenol	125
Figure 3 .88	Thermogram of CS-AM	126
Figure 3 .89	Thermogram of CS-PhALAM	127
Figure 3 .90	Thermogram of CS-APAM	128
Figure 3 .91	Thermogram of CS-RESAM	129
Figure 3 .92	Thermogram of CS-MEOXANAM	130
Figure 3 .93	DSC thermogram of chitosan	131
Figure 3 .94	DSC thermogram of CS-DCDA	132
Figure 3 .95	DSC thermograms of poly(1-vinylpyrrolidone-co-2-dimethylaminoethyl methacrylate) chitosan	133
Figure 3 .96	DSC thermogram of 4,7,10-trioxa-1,13-tridecanediamine chitosan	134
Figure 3 .97	DSC thermogram of CS-BCOE	134
Figure 3 .98	DSC thermogram of CS-PhAL	135
Figure 3 .99	DSC thermogram of CS-2AP	136
Figure 3.100	DSC thermogram of CS-APDCDA	137

Figure 3.101	DSC thermograms of CS-RES	138
Figure 3.102	DSC thermogram of CS-HQ	139
Figure 3.103	DSC thermogram of CS-mPhenol	140
Figure 3.104	DSC thermogram of polyacrylamide chitosan	141
Figure 3.105	DSC thermogram of phenylalanine polyacrylamide chitosan	142
Figure 3.106	DSC thermogram of CS-APAM	143
Figure 3.107	DSC thermogram of CS-RESAM	144
Figure 3.108	DSC thermogram of CS-MEOXANAM	145
Figure 3.109	SEM images of (a) chitosan, (b) CS-DCDA, (c) CS-VPDMAEM, (d) CS-OXAM, (e) CS-BCOE, (f) CS-PhAL, (g) CS-2AP, (h) CS-APDCDA, (i) CS-RES, (j) CS-HQ, (k) CS-mPhenol, (l) CS-AM, (m) CS-PhALAM, (n) CS-APAM, (o) CS-RESAM, and (p) CS-MEOXANAM.	148
Figure 3.110	The X- ray diffraction spectra of (a) chitosan, (b) CS-DCDA, (c) CS-VPDMAEM, (d) CS-OXAM, (e) CS-BCOE, (f) CS-PhAL, (g) CS-2AP, (h) CS-APDCDA, (i) CS-RES, (j) CS-HQ, (k) CS-mPhenol, (l) CS-AM, (m) CS-PhALAM, (n) CS-APAM, (o) CS-RESAM, and (p) CS-MEOXANAM.	150
Figure 3.111 (a) and (b)	The solid state photoluminescence spectra for chitosan and chitosan derivatives	151
Figure 3.112	The inhibition percentage of cell viability for chitosan derivatives at neutral pH	158
Figure 3.113	Dose-dependent anti-proliferative effect of compound CS-HQ against PC3, MCF-7, HCT-116 and CCD-18Co (Values are represented as mean \pm SD, n=3)	159
Figure 3.114	Photomicrographs depict the images of cancer cell lines (PC3, MCF-7, and HCT-116) and normal cell CCD-18Co treated with CS-HQ taken under inverted microscope at 20X	160

LIST OF SCHEMES		Page
Scheme 1.1	N-alkylation of chitosan using reductive amination approach	10
Scheme 1.2	Quaternization of chitosan with methyl iodide	10
Scheme 1.3	N-acylated derivatives of the chitosan formed through the anhydrides, acid chloride interaction	11
Scheme 1.4	N, O acylated chitosan by the combination of hydrophobic groups	12
Scheme 1.5	N sulfonation of chitosan with 2-sulfobenzoic acid anhydride	12
Scheme 1.6	Graft copolymerization of methacrylic acid on hydroxypropyl chitosan	13
Scheme 1.7	Reaction of chitosan in aqueous acidic medium with using APS as initiator	14
Scheme 2.1	Reaction of dicyandiamide derivative of chitosan (CS-DCDA)	33
Scheme 2.2	Reaction of 2-aminopyridine dicyandiamide derivative of chitosan (CS-APDCDA)	34
Scheme 2.3	Reaction of poly(1-vinyl pyrrolidone-co-2-dimethylamino ethyl methacrylate) derivative of chitosan (CS-VPDMAEM)	34
Scheme 2.4	Reaction of 4, 7, 10-trioxa-1, 13-tridecanediamine derivative of chitosan (CS-OXAM)	35
Scheme 2.5	Reaction of bis(2-chloroethyl) ether derivative of chitosan (CS-BCOE)	36
Scheme 2.6	Reaction of l-phenylalanine derivative of chitosan (CS-PhAL)	37
Scheme 2.7	Reaction of 2-aminopyridine derivative of chitosan (CS-2AP)	37
Scheme 2.8	Reaction of resorcinol derivative of chitosan (CS-RES)	38
Scheme 2.9	Reaction of 8-hydroxyquinoline derivative of chitosan (CS-HQ)	38

Scheme 2.10	Reaction of 4-methylphenol derivative of chitosan (CS-mPhenol)	39
Scheme 2.11	Reaction of polyacrylamide derivative of chitosan (CS-AM)	39
Scheme 2.12	Reaction of l-phenylalanine polyacrylamide derivative of chitosan (CS-PhALAM)	40
Scheme 2.13	Reaction 2-aminopyridine polyacrylamide derivative of chitosan (CS-APAM)	41
Scheme 2.14	Reaction resorcinol polyacrylamide derivative of chitosan (CS-RESAM)	41
Scheme 2.15	Reaction 4-methoxyaniline polyacrylamide derivative of chitosan (CS-MEOXANAM)	42

LIST OF SYMBOLS

ppm	Parts-per-million
λ	Wavelength
cm	Centimetre
T	Temperature
μg	Microgram
$^{\circ}\text{C}$	Degree Celsius (centigrade)
mg	Milligram
kDa	Kilodalton
W	Mass
H	Hour
V	Volume
β	Beta
a.u	Arbitrary unit for intensity
nm	Nanometre
mL	Millilitre

LIST OF MAJOR ABBREVIATIONS

APS	Ammonium persulphate
C-1-6	Carbon number 2, 3, 4, 5 and 6
CAN	Ammonium cerium (IV) nitrate
CCD-18	Normal Fibroblast
CLSI	Clinical and Laboratories Standards Institute
COSY	Correlation spectroscopy
CS-2AP	2-Aminopyridine chitosan
CS-AM	Polycrylamide chitosan
CS-APAM	2-Aminopyridine polyacrylamide chitosan
CS-APDCDA	2-Aminopyridine dicyandiamide chitosan
CS-BCOE	Bis (2-chloroethyl) ether chitosan
CS-DCDA	Dicyandiamide chitosan
CS-HQ	8-Hydroxyquinoline chitosan
CS-MEOXANAM	4-Methoxy aniline polyacrylamide chitosan
CS-mPhenol	4-Methyl phenol chitosan
CS-OXAM	4, 7, 10-Trioxa-1, 13-tridecanediamine chitosan
CS-PhAL	L- phenylalanine chitosan
CS-PhALAM	L-Phenylalanine polyacrylamide chitosan
CS-RES	Resorcinol chitosan
CS-RESAM	Resorcinol polyacrylamide chitosan
CS-VPDMAEM	Poly (1-vinyl pyrrolidone-co-2-dimethyl amino ethyl methacrylate) chitosan
DA	Degree of acetylation
DD	Degree of degradation
DMSO	Dimethyl sulfoxide
DOX-GC	Doxorubicin conjugated glycol chitosan
DPPC	Dipalmitoyl phosphatidylglycerol
DSC	Differential scanning calorimetry
<i>E. coli</i>	<i>Escherichia coli</i>
EAT	Ehrlich ascites tumor
EPR	Enhanced permeability and retention

FT-IR	Fourier transform infrared spectroscopy
GPC	Gel permeation chromatography
HCT-116	Colon cancer cell line
HepG2	Human liver hepatic cellular carcinoma cell line
HIFBS	Heat-inactivated fetal bovine serum
HMQC	Heteronuclear multiple-quantum correlation
IC50	Median inhibitory concentration
KPS	Potassium persulphate
L1210	Murine leukemia
M5076	Murine liver metastatic tumor
MAS	maleic acid sodium
MCF-7	Breast cancer cell line
Md	Molecular weight of organic compounds before reacted with chitosan
MH134	Murine hepatic cell carcinoma
MHA	Mueller-Hinton agar
MIC	Minimum inhibitory concentration
MMC	Mitomycin C
Mn	Number-average molecular weight
MTT	(3-(4, 5-dimethylthiazol-2-yl) - 2,5 diphenyl tetrazolium bromide)
Mw	Weight-average molecular weight
Mz	Size-average molecular weight
Mz/Mw	Polydispersity index
NMR	Nuclear magnetic resonance
OM	Outer membrane
PC3	prostate cancer line
PEG	Polyethylene glycol
PL	Photoluminescence
RAW 264.7	Mouse monocyte macrophage
<i>S. aureus</i>	<i>Staphylococcus aureus</i>
SEM	Scanning Electron Microscopy
SMMC-7721	Human hepatocellular carcinoma cells

T_g	Glass transition temperature
TGA	Thermogravimetric analysis
XRD	X-Ray diffraction

PENYEDIAAN DAN PENCIRIAN TERBITAN KITOSAN TERLARUT AIR DENGAN BEBERAPA AKTIVITI BIOLOGI

ABSTRAK

Tujuan penyelidikan ini adalah untuk mensintesis terbitan kitosan larut air yang baru, serta mengkaji sifat fizik dan sifat kimia, mereka disamping sifat antibakteria dan antikanser. Justeru, 14 terbitan kitosan disintesis dengan julat berat molekul yang luas (daripada 0.56 hingga 220 kDa). Pelbagai kumpulan berfungsi, iaitu fenilnilina, benzena-1,3-diol, metilfenol, 8-hidroksikuinolina, 2-aminopiridina, (bis(2-kloroetil) eter, 4,7,10-trioksa-1,13-tridekanadiazina, disiandiamida, akrilamida dan poli(1-vinilpirolidon-ko-2-dimetilaminoetilmetakrilat telah digunakan untuk menghasilkan kitosan yang terubahsuai. Terbitan ini dicirikan dengan menggunakan pelbagai teknik alatan seperti spektroskopi inframerah transformasi Fourier (FT-IR), spektroskopi resonan magnetik nuklear (NMR) (proton dan karbon-13), analisis termogravimetrik (TGA) dan kalorimetri pengimbasan pembezaan (DSC). Kebanyakan terbitan ini menunjukkan keterlarutan dalam keadaan neutral dan berasid. Terbitan kitosan menunjukkan darjah pendeasetilan yang lebih rendah daripada kitosan, dan keadaan hablur kitosan bertukar kepada amorfus selepas kumpulan berfungsi diperkenalkan. Kebanyakan terbitan juga menunjukkan sifat pendarcahaya yang menarik. Semua terbitan mempunyai kesan antiproliferatif yang berbeza terhadap tiga jalur kanser apabila ujian *in vitro* dijalankan, iaitu kanser prostat, kolon dan kanser payudara pada pH neutral. Terbitan 4,7,10-trioksa-1,13-tridekanadiazina kitosan menunjukkan ketoksikan yang rendah terhadap sel kanser payudara dengan $IC_{50} = 109.8 \mu\text{g mL}^{-1}$. Bis(2-kloroetil) eter kitosan menunjukkan aktiviti yang signifikan terhadap kanser payudara MCF-7 dengan $IC_{50} = 57.25 \mu\text{g}$

mL⁻¹. 8-Hidroksikuinolina kitosan menunjukkan kesan antiproliferatif yang amat tinggi terhadap jalur sel kanser yang diuji, iaitu jalur sel kanser prostat PC3 dengan IC₅₀ = 12.11 µg mL⁻¹, jalur sel kanser payudara MCF-7 dengan IC₅₀ = 14.18 µg mL⁻¹ dan jalur sel kanser kolon HCT-116 dengan IC₅₀ = 79.21 µg mL⁻¹. Sifat antibakteria terhadap bakteria gram-negatif, iaitu *E. coli* dan bakteria gram-positif, iaitu *S. aureus* menunjukkan. Kepekatan Perencatan Minimum (MIC) pada 1000 µg mL⁻¹. Namun demikian, kebanyakan terbitan kitosan menunjukkan nilai MIC yang lebih rendah, iaitu dari 500 hingga 62.5 µg mL⁻¹.

PREPARATION, CHARACTERIZATION AND SOME BIOLOGICAL ACTIVITIES OF WATER SOLUBLE CHITOSAN DERIVATIVES

ABSTRACT

The aim of this research is to synthesise novel water-soluble chitosan derivatives and to investigate their physical, chemical as well as antibacterial and anticancer properties. Thus, fourteen chitosan derivatives were synthesised with a wide range of molecular weights (from 0.56 to 286 kDa). Various functional groups, i.e. phenylaniline, benzene-1,3-diol, methylphenol, 8-hydroxyquinoline, 2-aminopyridine, (bis(2-chloroethyl)ether, 4,7,10-trioxa-1,13-tridecanediamine, dicyandiamide, acrylamide, poly(1-vinylpyrrolidone-co-2-dimethylaminoethyl methacrylate) were used to produce the modified chitosans. These derivatives were characterized using various techniques such as Fourier transform infrared spectroscopy (FT-IR), nuclear magnetic resonance spectroscopy (NMR) (proton and carbon-13) elemental analysis, thermogravimetric analysis (TGA) and differential scanning calorimetry (DSC). Most of these derivatives showed remarkable solubility in neutral and acidic conditions. The chitosan derivatives showed lower degree of deacetylation than chitosan, and the crystalline state for chitosan was changed to amorphous after the introduction of the functional groups. Most of the derivatives also showed interesting luminescent properties. All derivatives have different antiproliferative effect against three cancer lines when tested *in vitro* namely prostate, colon and breast cancer at neutral pH. The 4,7,10-trioxa-1,13-tridecanediamine chitosan derivative exhibited mild cytotoxicity against breast cancer cell with $IC_{50} = 109.8 \mu\text{g mL}^{-1}$. Bis(2-chloroethyl) ether chitosan showed significant activity against breast cancer MCF-7 with $IC_{50} = 57.25 \mu\text{g mL}^{-1}$. 8-

Hydroxyquinoline chitosan exhibits the highest antiproliferative effect against the tested cancer cell lines i.e., prostate cancer cell line PC3 with $IC_{50} = 12.11 \mu\text{g mL}^{-1}$, breast cancer cell line MCF-7 with $IC_{50} = 14.18 \mu\text{g mL}^{-1}$ and colon cancer cell line HCT-116 with $IC_{50} = 79.21 \mu\text{g mL}^{-1}$. Antibacterial properties against gram-negative bacteria namely *E. coli* and gram-positive bacteria namely *S. aureus* showed Minimum Inhibitory Concentration (MIC) at $1000 \mu\text{g mL}^{-1}$ for chitosan. However, most of the chitosan derivatives showed lower MIC values namely from 500 to $62.5 \mu\text{g mL}^{-1}$.

CHAPTER 1

INTRODUCTION

1.1 Chitosan

Chitosan is a natural polysaccharide polymer that is obtained from the partial deacetylation of chitin (Figure 1.1.a) [1]. Chitosan are high-molecular-weight and linear heteropolysaccharide compound that composed of a β (1 \rightarrow 4) linked to two monosaccharides, N-acetyl-D-glucosamine and D-glucosamine. The structure of chitosan can be observed in Figure 1.1.b. Chitosan consists of three types of reactive functional groups, which are an amino group at C-2, primary hydroxyl group at C-3 and secondary hydroxyl at C-6 positions, respectively [2, 3].

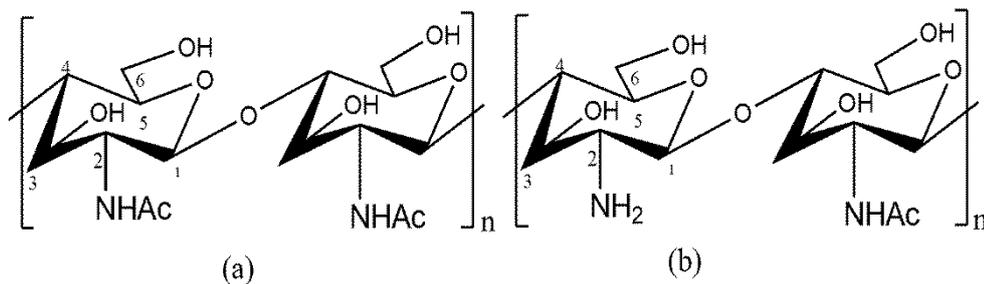


Figure 1.1 Structures of (a) chitin and (b) chitosan

In 1859, Rouge discussed the deacetylated form of chitosan by subjecting chitin to alkali treatment [4-6]. The interest on the use of chitosan has continued between 1930s to early 1940s [7]. In 1960s, a number of Asian nations such as Japan, Korea, Singapore, Taiwan, and Thailand were able to achieve ample amount of research that focused on better understanding of chitin and chitosan materials, and covering the whole spectrum of research from better production to the purification methods [5]. In 1970s, there was a resurgence of interest in chitosan [5, 6]. China has

joined these researchers and become an important producer of chitin and chitosan in Asia [5]. In the last few decades, chitosan has shown as a potential source of bioactive material and abundant of applications [8].

1.1.1 Production of Chitosan

The production of chitosan starts from the isolation of chitin from shells of crustaceans wastes of the seafood industries such as (shrimp, crab, and crawfish) (Table 1.1) [9,10]. These natural sources produced chitin amounting to a hundred billion tons each year [11].

Table 1.1: Contents of chitin from natural resources as reported by Kurita [10]

Source	Chitin (%)
Crab cuticle	15–30
Shrimp cuticle	30-40
Krill cuticle	20–30
Squid pen	20–40
Clam/oyster shell	3-6
Insect cuticle	5–25
Fungi cell wall	10-25

These wastes from the seafood industries composed of lipids as primary structural components, protein, inorganic salts, and chitin. They are initially crushed and filled as powder to initiate further heterogeneous processes (Figure 1.2) [9].

In the first approach, 5 % sodium hydroxide was added to the shells to dissolve the various proteins, leaving behind chitin, lipids and calcium salts (mainly as CaCO_3). Then the mixture was treated with 30 % hydrochloric acid to dissolve the calcium salts (demineralization). This step also hydrolyzes the lipids, dissolves other minor inorganic constituents and produces chitin. The obtained chitin is hydrolyzed at 100 °C in the presence of 50 % sodium hydroxide solution to produce chitosan [9].

In the second approach, 5 % hydrochloric acid was added to the shells powder to remove calcium salts. This step followed high-temperature (110 °C) treatment with 40 % sodium hydroxide to remove protein and lipids. During the treatment, a concomitant hydrolysis of acetamide groups in chitin has taken place, resulting in the formation of chitosan [1, 9].

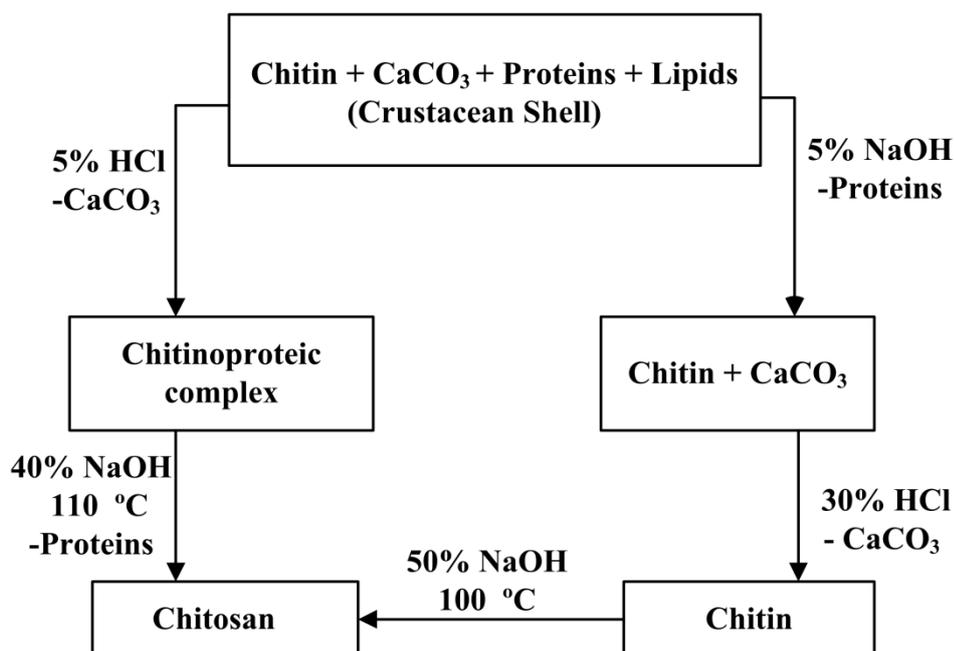


Figure 1.2 Isolation of chitin and synthesis of chitosan as reported by Olteanu [9]

1.1.2 Properties of Chitosan

The characteristics of chitosan and the final product performance are affected by many conditions such as the type and concentration of reagents, the time and the reaction temperature throughout the processing. The relevant parameters of the product are degree of deacetylation (DD) and molecular weight that influences the solubility, rheological and physical properties [8]. The variation in commercial chitosan grades is due to the difference in the DD and molecular weight. However,

the improvements in chitosan characteristics can be achieved through modifications of the DD and the molecular weight. For example, the value of DD can be decreased by deacetylation [12, 13] while the molecular weight can be reduced by acidic or enzymatic depolymerization [14, 15].

1.1.2.1 Molecular Weight

Molecular weight directly influences the chemical, physical and biological properties of chitosan, such as viscosity, solubility, adsorption on solids, elasticity and tear strength [8]. The effect of chitosan for biomedical applications comes not only from their chemical structure but also comes from the molecular weight [15]. It was observed that the crystallinity of chitosan increased with decrease in molecular weight [8]. The average molecular weight can range from 50 to 2000 kDa, depending on the preparation processes and the source [16, 17].

1.1.2.2 Degree of Deacetylation

The degree of deacetylation (DD) can be used to specify the variation of acetyl content for this family of polymer. The names chitin and chitosan correspond to acetyl content that is measured by the DD [8]. Deacetylation is the removal of acetyl groups from the chitin molecular chain, leaving behind amino groups (NH_2). Increasing the number of this amine group in chitosan requires repeated alkaline treatment to achieve high deacetylation (can be up to >90% [13]). Increasing the number of amine groups can also be done by increasing the temperature or the strength of the alkaline solution during the deacetylation reaction [8]. Its property is dependent on the ratio of 2-acetamido-2-deoxy-D-glucopyranose to 2-amino-2-deoxy-D-glucopyranose in the structural units and the content of free amino groups

and can be used to differentiate between chitin and chitosan [1]. If the percentage of 2-amino-2-deoxy-D-glucopyranose units in the component is more than 50%, it is termed chitosan. Conversely, when the percentage of 2-acetamido-2-deoxy-D-glucopyranose units is higher, the term chitin is used [7, 18]. Nevertheless, in 2002 and Tommeraas et al. [19] suggested that chitin with DD of 60% and above to be known as chitosan.

The degree of crystallinity in chitin and chitosan is a function of the degree of deacetylation. High DD will result in chitosan with high crystallinity [16]. Solubility in acidic solution and the crystallinity of chitosan shows a strong association with the value of DD [20]. Chitosan with different ranges of DD (40 to 98%) has been commercially produced [16, 17].

1.1.2.3 Solubility of Chitosan

Chitosan is a weak base, which is insoluble in water, alkali or aqueous solutions at pH value higher than 7 and also in most organic solvents. Chitosan has the ability to dissolve in certain inorganic and organic acids such as hydrochloric, nitric, acetic, phosphoric, propionic, succinic, tartaric, lactic, citric and formic acids at certain pH values after prolonged stirring [8, 16, 21-23]. Chitosan is insoluble in sulphuric acid because they can react to form a white crystalline solid of chitosan sulphate [23]. The variation of chitosan solubility in acids depends on the pK_a of these acids and their concentrations [8, 20].

The solution viscosity in all solvent system is affected by polymer concentration, temperature, counter-ion concentration and pH [8]. For example, solution at pH below 4 positive charge of protonated amino group in chitosan causing to enhance the electrostatic repelling between charged groups of similar charge,

leading to promotion of swelling of the chitosan network [20]. While solvent with pH of 5.2 generates chitosan with the unstable structure because the free amino groups compose intermolecular hydrogen bonds with the oxygen in an excess of NaOH [24]. For solution at pH value higher than 6.5, which is roughly equal to the pK_a of chitosan amino group, the phase separation happens with the increase in aggregate size and the chitosan obtained coagulates and is recovered as an amorphous solid [20, 25]. The free amino (NH_2) groups in chitosan chain forms conformational features through intramolecular and/or intermolecular hydrogen bonding and make it a cationic polyelectrolyte ($pK_a \approx 6.5$), making it soluble in acidic solutions below pH ~ 6.5 [20].

The major limitation of chitosan comes from the poor solubility at physiological pH (7.4), especially for biomedical applications where it is insoluble and ineffective as an absorption enhancer [26]. There are many improvements of chitosan solubility such as by reducing the molecular weight [14, 15, 23]. Different chemical modification techniques that involve introducing a hydrophilic functional group such as polyethylene glycol (PEG) have been employed in previous studies to produce water-soluble derivatives of chitosan [16, 19, 20, 23, 26, 27]. The recently good water solubility of modified chitosan has attracted the attention of many researchers such as O-quaternary ammonium N-acyl thiourea chitosan [7].

1.1.2.4 Viscosity

The viscosity of chitosan is an important factor in determining its commercial and biological applications. The viscosity of chitosan is proportional to the molecular weight and conversely with the demineralization time [28]. Moreover, it is affected by other factors during production processes such as the degree of deacetylation,

concentration of the solution, ionic strength, pH, and temperature. The intrinsic viscosity of chitosan depends on the degree of ionization more than the ionic strength [29]. This is confirmed by the variation of chitosan viscosity in acids such as in acetic acid. The viscosities increases with decreasing pH, In case of decrease pH by using HCl causes to lower the viscosity. It means depend of kind of acid used to decrease the pH. Bough et al. [29] and Moorjani et al. [28] have reported that the production of chitosan with 3% NaOH or acetone considerable decreases the viscosity of the final chitosan products. They concluded that chitosan viscosity is strongly affected by physical treatments such as grinding, heating, autoclaving and ultrasonication and showed that the decrease in viscosity with an increase in treatment time and temperature [30].

Bough et al. [29] investigated the effect of particle size on the viscosity of chitosan. They found that smaller particle size (1 mm) resulted in chitosan products of both higher viscosity and molecular weight than those of either 2 or 6.4 mm particle size, because the larger particles need more swelling time.

1.1.2.5 Biological Properties of Chitosan

Chitosan and its derivatives have appealing biological properties such as low toxicity, biodegradability, and biocompatibility. These properties lead to commercial production of chitosan and its derivatives for medical, pharmaceutical and industrial applications [31, 32, 33].

1.1.2.5.1 Biodegradability

Biodegradability is one of the most essential and valuable properties of chitosan and its derivatives. Usually, non-toxic oligosaccharides lengths can be

obtained from the biodegradation of chitosan that can be generated by using several techniques such as physical, enzymatic and chemical methods. Physical techniques such as ozone treatment and ultraviolet radiation accelerate the degradation of chitosan [34]. Enzymatically, chitosan can be degraded in vitro, by several non-specific enzymes such as lysozymes, pepsin, papain, cellulase, pectinase, proteases and lipases that are found in mammals [35, 36]. The oligosaccharides can be subsequently incorporated into glycosaminoglycans and glycoproteins metabolic pathways [16]. It believed that chitosan degrades invertebrates mostly by lysozyme and bacterial enzymes inside the colon [37].

Chitosan degradation is affected by the DD value and the distribution of their acetyl groups. The DD value that controls the degree of chitosan crystallinity is inversely proportional to degradation kinetics while reducing of acetyl groups or their homogeneous distribution caused very low rates of enzymatic degradation [38, 39]. The association of chitosan degradation and the DD value has been investigated in several studies, and all of them obtained the same inversely proportional relationship [12, 40, 42]. In 2005, Kofuji et al. [41] studied the effect of enzymes on chitosan degradation. They considered various chitosans viscosity in the presence of lysozyme solutions; finally they reported that chitosan with low DD degraded more quickly. Other studies mentioned that the variation in chitosan degradation can be attributed to the differences in the distribution of acetamide groups in the chitosan molecule [38, 41]. Differences of this distribution changes inter or intramolecular repulsion forces, which influences the viscosity of the chitosan solution [12].

1.1.2.5.2 Biocompatibility

Biocompatibility is one of the most attractive characteristics of chitosan. For example, the role of chitosan is not changed by host medium conditions and there are no any undesirable local or systemic effects have been recorded or observed due to changes in function of chitosan. In spite of the living tissues, including the skin, ocular membranes and the nasal epithelium showed real acceptance or well tolerated to chitosan. Biocompatibility characteristics also depend on the property of the origin of chitosan such as natural source, method of preparation, molecular weight (Mw), and DD [12].

1.1.2.5.3 Toxicity

Chitosan has very low toxicity when compared with other natural polysaccharides. Chitosan showed lethal dose LD50 around 16 g kg^{-1} , very close to the value obtained for salt and glucose carried out in the laboratory by *in vivo* toxicity assays [42]. In an earlier study, it was found that the toxicity of chitosan is strongly correlated with the DD value. It is reported that chitosan with DD values higher than 35% exhibited low toxicity while chitosan with DD value under 35% showed dose-dependent toxicity [34].

1.2 Previous Studies on Modification and Applications of Chitosan


This section presents the previous studies and survey of the relevant literature on the chemically modified chitosan and its applications.

1.2.1 Chemically Modified Chitosan


Chemically modified chitosan has been extensively explored and can be considered as the most important method to improve the water solubility of chitosan by adding some hydrophilic functional group [43, 44]. The synthetic methods of chitosan derivatives reported in the literature falls under one of the three categories; N-alkylation, N and/or O acylation and grafting of chitosan.

1.2.1.1 Alkylated Derivatives of Chitosan

N-alkylated chitosan has been prepared by reacting aldehydes or ketones (the Schiff reaction) with the amino groups of chitosan. Then addition of borohydride NaBH_4 or sodium cyanoborohydride NaBH_3CN to reduce imines formed to amines as shown in Scheme 1.1 [44 - 46]. It has also been reported that N-alkylated chitosan could be obtained by the reaction of alkyl bromide [47] or alkyl iodide [48] with amino groups of chitosan, leading to quaternary ammonium formation as shown in Scheme 1.2. Domard et al. [49] used this approach to generate a wide pH range of water soluble cationic derivatives.

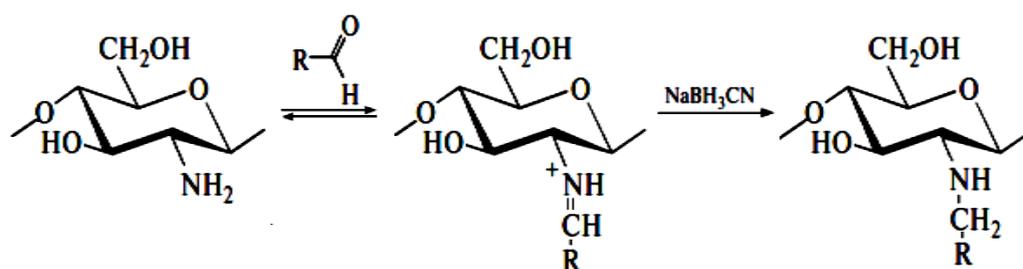


Scheme 1.1: N-alkylation of chitosan using reductive amination approach

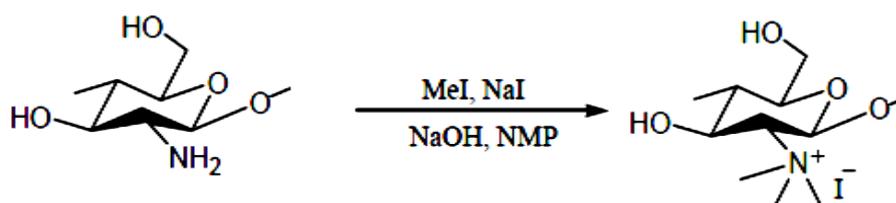

Scheme 1.2 Quaternization of chitosan with methyl iodide

1.2.1.2 Acylation Derivatives of Chitosan


Derivatization by acylation has more synthetic pathways compared to N-alkylation because hydrophobic groups can react with N or O atoms or to both atoms at the same time. Aranaz et al. [45] reported that the derivatization of chitosan by a hydrophobic group is formed via an ester bond that can be considered as the enzymatic actions. They noted that the chitosan derivatives were randomly distributed along the chain, through alkylation or acylation under homogeneous conditions. Various works were successful in the preparation of N-acylated derivatives of chitosan through the anhydrides, acid chlorides interaction with the amino groups of chitosan as shown in Scheme 1.3.

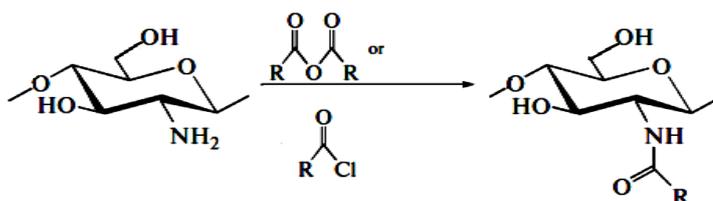

Scheme 1.3: N-acylated derivatives of the chitosan formed through the anhydrides, acid chloride interaction

In the preparation of O substituted derivatives, it is necessary to keep the amino group in positive charge thus it works well in an acidic solution. The activity of amino groups is higher than the hydroxyl groups, consequently amino groups are blocked prior to O acylation, such as in the reactions with acid chlorides in methane sulfonic acid as shown in Scheme 1.4 [50]. N, O acylated chitosan reported in prior works followed by steps procedure, the first step chitosan O acylation by blocking amino groups. The second step involves protection of amino groups removed and continued with N-acylation synthesis [45, 51, 52]. Riva et al. [53] and Aranaz et al. [45] described the synthesis of N; O acylated chitosan compounds in their reviews.


They refer to various methods that have been used to prepare hydrophobic derivatives of chitosan by the combination of hydrophobic groups into chitosan chains.

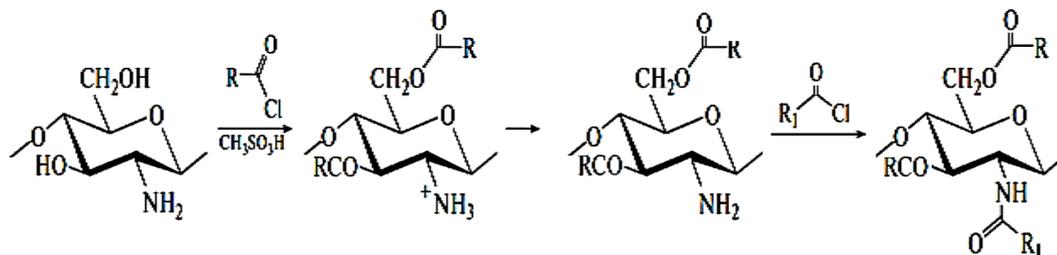

Scheme 1.4: N, O acylated chitosan by the combination of hydrophobic groups

1.2.1.3 Thiolation of Chitosan

Anionic charge can be introduced to the basic structure of the chitosan polymer, by the reaction of chitosan with 2-sulfobenzoic acid anhydride as shown in Scheme 1.5 [54]. Jayakumar [55] reported the chemical modification of chitosan with sulfate produced novel bifunctional materials that are promising for biomedical applications.

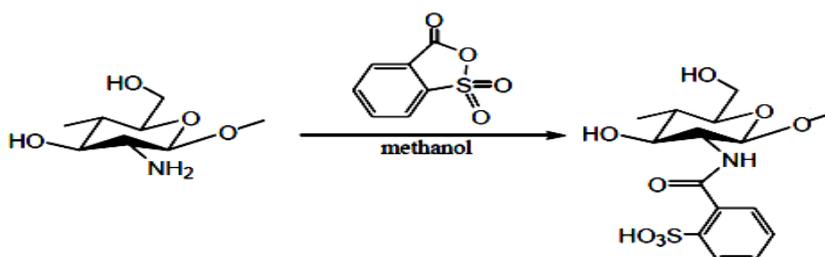


Scheme 1.5: N sulfonation of chitosan with 2-sulfobenzoic acid anhydride

1.2.1.4 Grafting of Chitosan

Many studies have been carried out on the grafting of polysaccharide based materials to improve properties for the biomedicine and environmental field of applications [56, 57]. Several investigations have been reported on the study of


grafting natural polymers by using radiation for example as reported by Jaafar et al. [58] and Pengfei et al. [59]. Enzymatic grafting in several previous works described some advantages of synthesis and modification of polymers by using enzymes [60]. Ilyina et al. [61] reported that enzymatically modified polymers such as partially hydrolyzed chitosan can be obtained with similar biochemical properties compared to chitosan. Chitosan has also been grafted through the addition of cationic polymerization as reported by Yoshikawa et al. [62] They have performed grafting reaction by introducing poly (isobutyl vinyl ether) and poly(2-methyl-2-oxazoline) cation onto the amino groups in the chitosan. Recently, grafting of vinyl monomers through free radical initiation has attracted the interest of several researchers. This approach offered wider options with new structures and preferred properties. Sun et al. [63] used ammonium persulphate (APS) as an initiator in an aqueous solution to prepare carboxymethyl chitosan grafted methacrylic acid. Similarly, Xie et al. [64] succeeded in producing hydroxypropyl chitosan grafted methacrylic acid as shown in Scheme 1.6, which exhibited more improvement in water solubility.

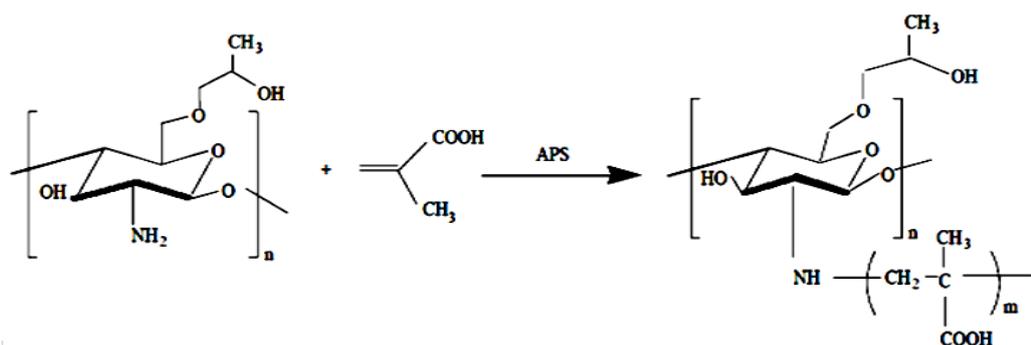

Scheme 1.6: Graft copolymerization of methacrylic acid on hydroxypropyl chitosan.

Sun et al. [65] used APS initiator to graft copolymerization of maleic acid sodium (MAS) onto carboxymethyl chitosan and hydroxypropyl chitosan and reported that the reaction conditions played a critical role in the grafting

copolymerization. The polymerization of aniline was obtained by the reaction of aniline in the presence of APS with chitosan. In this reaction (Scheme 1.7) the polyaniline side chains are bonded with the chitosan amino groups [66].

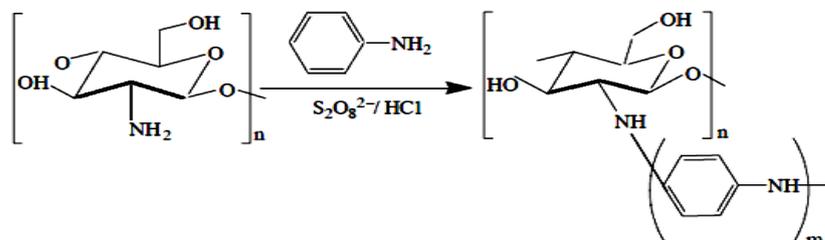

Scheme 1.7 Reaction of chitosan in aqueous acidic medium with using APS as initiator [66]

Graft copolymerization of vinyl monomers onto chitosan is also carried out using redox initiator systems, such as ceric ammonium nitrate (CAN) and potassium persulphate (KPS). This approach was reported for the first time in 1958 by Mino and Kaizerman. [67] They employed a ceric ion redox initiating system to achieve copolymer grafting. After that, this approach witnessed magnificent development [68] especially in the case of cellulose [69] and starch [70]. Usually, this method produced grafted copolymers with medium to the high molecular weight that are spaced along the backbone of the polysaccharide [69].

In previous studies, some organic compounds were reacted with chitosan, such as amino acid and amino acid derivatives, aniline, phenol, ether and heterocyclic to modify chitosan. Layek and Singh [71] synthesized n-acetylamino and amino acids through coupling reaction of mediated carbodiimide which can be used in gene treatment. Zhang et al [72] introduced an oral delivery method of insulin by using N-octyl-N-arginine chitosan micelles. Yamada [73] has grafted hexyloxyphenol onto chitosan by using an enzymatic method. Yang and Yuan [74]

synthesized chitosan hydroxyl azacrown ether from the reaction of hydroxyl azacrown ether with epoxy-activated chitosan. Many heterocyclic compounds have been reacted with chitosan as reported by Badawy [75], such as heterocyclic aldehydes containing 3-pyridine carboxaldehyde, 5-methylfuran-2-carbaldehyde, furan-2-carbaldehyde and benzo[d] (1,3). The various techniques to prepare chitosan derivatives are shown in Figure 1.3 [76].

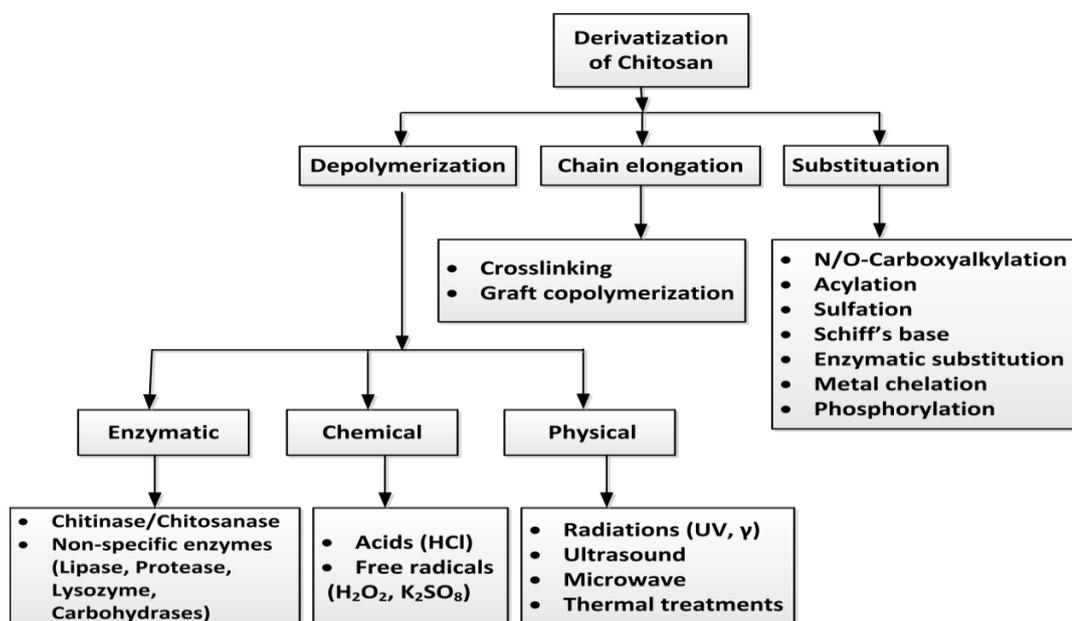


Figure 1.3: Techniques for derivatization of chitosan [76]

1.3 Applications of Chitosan

Chitosan and its derivatives have different practical properties, which make them appropriate for many applications such as in agriculture, food, wastewater management, cosmetics, fiber and biomedicine [7, 9]. The wide variation of chitosan molecular weights and degree of deacetylation, give opportunities to use it in different cosmetic fields such as skin care, water-resistance, sun protection, deodorants and hair care [5, 25]. Chitosan is also used for biomedicine applications; clinical studies have found 3-6 grams per day of chitosan can be used with no

adverse effects [9, 64]. Therefore, chitosan attracts lots of attention for the pharmaceutical formulation and different medical applications in topical and ocular applications, implantation or injection focusing on its biocompatible, absorption-enhancing, controlled release and bioadhesive properties [5]. Furthermore, chitosan can be considered as biodegradable, metabolized by some human enzymes, such as lysozyme and bioadhesive [77]. Carreno-Gomez [78] reported that chitosan extensively used for oral and intranasal delivery parenteral drug delivery. Chitosan has been used as starting material for man-made fibers, filament, powder, granule, sponge, absorbable sutures in medical products, composite with cotton or polyester and wound dressing materials. It could be considered for skin replacement [79] and antitumor effect through the proliferation of cytolytic T-lymphocytes [1, 32].

Chitosan can attach itself to fat in the stomach before it is digested, and it has no calorie value, making it good fat trapper for a weight loss products [1, 7]. Additionally chitosan and its derivatives have been used in the large area of biological fields such as an antibacterial, antifungal agent, to suppress viral infections in various biological systems, plants, animals and humans. Chitosan is also used for wound dressing materials [1, 7, 22, 23].

1.3.1 Anticancer Properties

Chitosan has direct effects on cancer cells by interfering with cell metabolism, stop cell generation, or stimulate cell apoptosis. It plays antitumor role by developing the resistant and protections of body functions. Many previous works *in vitro* and *in vivo* suggested that chitosan is very appropriate for complementary antitumor for drug and drug delivery applications [80, 81]. These studies discovered the significant changes in the antitumor activity of chitosan nanoparticles from

variable manufacturers and the quality of chitosan nanoparticles for particular cancer cell [82]. Maeda and Kimura [80] reported that chitosan with low molecular weight and chitosan oligosaccharide successfully stopped growing cancer cells in Sarcoma 180 - bearing mice. Torzsas et al. [81] have established that a diet including chitosan can decrease the growth of the cells containing precancerous lesions especially in colon cancer caused by azomethane compounds. In an other study, it was found that inhibition rates for different types of cancer cell lines (23 % of liver SMMC-7721 cells, 27 % of Hela cells of cervical cancer, 7721 cells, 29 % of gastric cancer BGC-823 cells 23 % on liver SMMC), and as high as 55 % of breast cancer MCF-7 cells, when treated with 500 mg L⁻¹ chitosan nanoparticles [83].

Nanoparticles of carboxymethyl chitosan with high toxicity can be grafted from doxorubicin/methoxy polyethylene glycol (PEG). These nanoparticles have been found to stop the distribution of cancer cells effectively [84]. In addition, nanoparticles of paclitaxel chitosan have also exhibited sustained release influence with good encapsulation percentage of 94.0% ± 16.73% [85]. Qi et al. [86] have applied high surface charged nanoparticles of chitosan to human hepatoma BEL7402 cells *in vitro* and found that dose and time correlation with anticancer activity. Hosseinzadeh et al, [87] prepared nanoparticles of gemcitabine-loaded via an ionic gelation technique, by using Pluronic RF-127 with chitosan nanoparticles as a carrier of cytotoxicity on HT-29 colon cancer cell line and found the inhibition of cancer cell on HT-29 colon carcinoma cell. Similarly, chitosan–silica hollow nanospheres were studied (CS–SiO₂ HNPs) for breast tumor cells MCF-7 treatment *in vitro* and *in vivo* environments with high therapeutic effectiveness [88]. Ignacak et al. [89] reported the microcrystalline structure inhibition of Ehrlich ascites tumor (EAT) cells. Huang et al. [90] reported that cytotoxicity on human lung carcinoma cell line

A549 (*in vitro*) showed insignificant effect when molecular weight of chitosan is decreased. Jiang et al. [91] confirmed that tailored chitosan can stop cell production and make apoptosis in MCF-7 breast cancer cell line. Dou et al. [92] found that oligochitosan effectively contribute to the apoptosis of HL-60 and similar behavior has been observed by Xu et al. [93] for chitooligosaccharides when used for human hepatocellular carcinoma cells (SMMC-7721 cells). Kumar et al. [94] studied the anticancer and antimicrobial effect of a new chitosan thymine conjugate prepared via acylation reaction between chitosan and thymine-1-yl-acetic acid and reported that the chitosan thymine conjugate considerably decreased the production of tumorous human liver hepatic cellular carcinoma cell line HepG2 cells with non-cytotoxic effect. Positive results of using chitosan as anticancer material have been reported by Hossain and Takahashi [95] and Hwang et al. [96] for improving the apoptosis in the human colon adenocarcinoma, HT-29 cells and prevent tumor of mouse monocyte-macrophage, RAW 264.7 cell line respectively. It has also been used for bladder cancer [97] and colon cancer [98]. Yamada and Clark [99] investigated the effect of chitosan on the Ehrlich ascites tumor (EAT) cells via nucleosomal DNA obliteration. Chitosan has also been used for prevention as proposed by Shen et al. [100]. They showed that chitosan has negative influence on the increase of HepG2 cells and destroys cancer cell growth in HepG2-carrier mice.

The amino group in chitosan under acidic medium is responsible for the mucoadhesive properties and increase the residual time at the absorption site. This makes chitosan nanoparticles an effective carrier for the oral absorption of drugs [101, 102]. Ringdorf [103] introduced the concept of using polymer nanoparticles for delivering small molecule drugs to their site of action in 1975. Based on this concept, several works successfully applied to use chitosan-anticancer drug conjugates, such

as doxorubicin conjugated glycol chitosan (DOX-GC) with a cis-aconite spacer [104] and n-lauryl-carboxymethyl which was used as carrier for hydrophobic cancer drugs [105].

The chitosan-based nanoparticles were found to accumulate preferentially in the tumor tissue known as EPR (enhanced permeability and retention) effect [105]. These chitosan byproducts have the capacity to solubilize taxol micelles to be therapeutically useful. Another chitosan-based polymeric micelle for taxol delivery in cancer therapy has been tested by Zhang et al. [106]. They obtained new N-alkyl-O-sulphated chitosan that could be considered as useful taxol for drug carrier. N-succinyl-chitosan derivatives conjugated have also shown good antitumor activities with mitomycin C (MMC) [107]. These chitosan-based conjugates were also proven to have good action against murine leukemia (L1210 and P338), B16 melanoma, murine liver metastatic tumor (M5076, Sarcoma 180 solid tumor) and murine hepatic cell carcinoma (MH134). Tan et al. [108] reported interesting results of chitosan as anticancer drug conjugates. This is attributed to the excellent properties of chitosan, and its use as nanoparticle for drug delivery systems.

1.3.2 Antimicrobial Activity of Chitosan

Many antimicrobials materials such as sulfite, benzoate, sorbate were employed as reliable stabilizers to control microbial contaminants and risks in food manufacturing for decades [109]. These synthetic materials are not considered healthy foods; consumers are looking for safer and preferably natural antimicrobials. Chitosan has attracted much attention as the natural substitution material and offers a wide variety of antimicrobial activity including bacteria, yeast, and fungi [110]. Moreover, it exhibits more advantages relative to other natural antimicrobials, such

as better antimicrobial properties, a wider range of the behavior spectrum, greater killing extent and minor mammalian cells toxicity [110].

Several mechanisms can explain the antimicrobial activity of chitosan. Nikaido [111] reported that the gram-negative bacteria are more resistant to amphiphilic and lipophilic inhibitors compared with the gram-positive bacteria. Chitosan cannot pass through the external layer of gram-negative bacteria. However, the positive charge of the chitosan molecule which comes from the amino group at C-2 below its pK_a (pH 6.3), creates the polycationic structure of chitosan. This polycationic structure interacts with the predominantly anionic components of the gram-negative surface such as proteins and lipopolysaccharides. According to Helander et al. [112] the polycationic chitosan binding of outer membrane (OM) of gram-negative bacteria caused to interrupt and loss barrier function of the OM. The antibacterial activity of chitosan obtained from the interface of chitosan's positive charges with the macromolecules negative charges at the bacterial cell surface, which changes the cell permeability [113, 114].

Sudarshan et al. [114] studied the mechanism of antibacterial activity of chitosan by referring to the binding of the amino group of chitosan to the surface components of bacteria. Chitosan cause cell death due to leakage of intracellular components at lower concentrations (0.1 mg mL^{-1}). Additional coating of the bacterial surface can be achieved at a higher level (2.0 and 5.0 mg mL^{-1}). This effect can stop the leakage of intracellular components as well as to impede mass transfer across the cell barrier [115]. Helander et al. [112] reported experimental confirmation about the mechanism of antibacterial activity of chitosan namely *E. coli*, *P. aeruginous* and *S. Typhimurium* by using electron microscopy. It is clear that chitosan disrupts the barrier properties of the outer membrane of gram-negative

bacteria. The electron micrographs demonstrated that site action of the chitosan is at the outer membrane (OM) of bacteria. Similar experimental results were stated by Coma et al. [115] for the bactericidal activity of chitosan on bacteria like *L. innocua*. They attributed the action to the interface of positively charged of chitosan with the negatively charged of the bacterial cell surface.

Previous studies on the activity of chitosan with biological membranes cannot sufficiently explain the electrostatic interactions of the protonated amino groups at low pH [116]. Another study mentioned that hydrophobic interactions have an important role in the polysaccharide action. In the investigation, the effect of pH and molecular weight of chitosan showed that increasing molecular weight (213 kDa) and decreasing pH can lead to disruption of the membrane [117]. The ionization of the amino groups of chitosan increases the antimicrobial activity of chitosan with decreasing pH to below 6 [10, 19, 23]. At pH 7, unmodified chitosan is not antimicrobial active because it does not dissolve and does not contain any positive charge [21, 118]. The antimicrobial activity of water-soluble chitosan derivatives depended on the degree of deacetylation and the substituted group [118].

A study has shown that anti-fungal and bactericidal activities of chitosan can be due to the ability of chitosan to interrupt the inner and outer membranes of the cells [119]. The role of electrostatic, hydrophobic and hydrogen bond in the interactions between chitosan and three different lipids has been investigated using Langmuir films to mimic the interaction between chitosan and bacterial membranes [120]. The results showed that the effect of chitosan on dipalmitoyl phosphatidylglycerol (DPPG) can be negligible [120]. This effect was found to decrease with increasing pH, due to the charge-mediating action of chitosan, whereas

pH did not affect the cholesterol monolayers where interactions occur mainly via hydrogen bonding.

1.3.2.1 Determination of Chitosan Antimicrobial Activities

Antimicrobial activities of chitosan were obtained by three methods, namely agar dilution, broth microdilution and disk diffusion. These techniques are recommended by Clinical and Laboratories Standards Institute (CLSI) as standard methods *in vitro*, to determine the sensitivity of bacteria applied as antimicrobial agents (CLSI, 2009; CLSI, 2009) [121]. Disk diffusion technique tests a large number of antimicrobials separately in a comparatively easy and cheap way and the results can be considered as qualitative since it can only show the sensitivity of antimicrobials against the bacteria tested, which is defined as susceptible, intermediate, and resistant that is associated with diameter of inhibition region. The disk diffusion technique can not determine the minimum inhibitory concentration (MIC), also it is hard to test the susceptibility of fastidious and slow-growing bacteria [122]. Besides, it is labor-intensive and time-consuming, in the same manner as other agar-based techniques [123].

Many reported works used disk diffusion to define the antimicrobial activities of chitosan [123-126]. Moreover, this technique is not always dependable for determining the antibacterial activity of natural antibacterial due to the polarity of the natural compounds that can affect the diffusion of compounds onto the culture medium [15].

Agar dilution technique is a quantitative susceptibility testing method using two-fold dilutions of an antibiotic made in Mueller-Hinton agar (MHA) medium and after that bacterial suspensions were inoculated on MHA [121].

The advantages of this method are that it can investigate the weaknesses of a number of bacteria in one plate and can test the fastidious microorganisms, and the agar can upkeep the bacteria growth sufficiently at the same time. Moreover, the agar dilution method is not usually used in most microbiology laboratories as it is costly, need intensive work and time-consuming. Broth microdilution technique is also a quantitative method normally employed in medical test centers and laboratories. This technique can also investigate the effects of numerous antimicrobials at the same time. Additionally, this method is highly saving in media usage, requires a small amount of testing sample and less time-consuming compared to the agar-based technique [127].

Both agar dilution and broth microdilution techniques can be applied to define MIC value. Earlier work reported that broth microdilution showed less MIC values than agar dilution for 47 gram-negative bacteria [127]. However, many studies have been done to compare the agar dilution and broth microdilution in antibiotic susceptibility testing and found a real association between them [127, 128]. Luber et al. [127] suggested that the broth microdilution method would be suitable and fast screening method for MIC determination as compared to the other methods. Based on a rather recent study, broth microdilution method can be recommended as a quick screening method for MIC determination. However, presently there are few studies on the evaluation of methodologies used for measuring the antimicrobial activity of chitosan, indicating that continuation of our study is needed for future work. However, in this research, MIC was determined by the broth microdilution method.

A broad range of MIC for chitosan to be used as antimicrobial material ranging from 0.005 % to 1.5 % (w/v) [129, 130, 131] has been reported. High

concentration of chitosan (1-1.5 %) showed complete inhibition of *S. aureus* after two days of incubation [132], while in another work chitosan concentrations lower than 0.005 % was enough to achieve deactivation of *S. aureus* [131]. To hamper the growth of *B. cereus* 0.02 % of chitosan was considered necessary as stated by Simpson et al. [132], Daramdji and Izumimoto [133] reported that for *E. coli* inhibition 0.1 % concentration of chitosan in meat protection, while another work reported that 0.0075 % of chitosan was adequate to stop the intensification of *E. coli* [131]. Moreover, at pH 5.5 chitosan with concentrations of 0.5 or 1 % can totally deactivate the growth of *E. coli* [134]. Besides, No et al. [130] reported that the growth of *L. monocytogenes* and *V. para haemolytic* us were completely inhibited by applying 0.1 % concentration of chitosan with molecular weight of 746 kDa and 470 kDa, respectively.

1.3.2.2 Factors Affecting the Antimicrobial Activity

Several factors affect the antimicrobial activity of different chitosans. These factors include two categories, i.e., intrinsic and extrinsic factors, such as Mw, DD, concentration, viscosity, solvent, pH, test strains, temperature and metal ions [3]. Moreover, the variation of application methodologies is an additional important factor that changed the results of chitosan antimicrobial activity.

1.3.2.2.1 Intrinsic Factors

In spite of numerous investigations the intrinsic and extrinsic factors influencing the activity of chitosan in antimicrobial applications, it is still a great challenge to identify the effect of the DD or molecular weight on this activity. For example, chitosan showed greater antimicrobial competence against gram-negative